


Showcasing research from Department of Catalysis, Chemistry Technology Center, Tarragona, Spain.

Facile synthesis of NHC-stabilized Ni nanoparticles and their catalytic application in the Z-selective hydrogenation of alkynes

Make it easy selecting the right NHC precursor! In their communication on page 7894, Miriam Díaz de los Bernardos, Carmen Claver, Cyril Godard and co-workers describe a new and straightforward methodology for the preparation small and well defined NHC-stabilized nickel nanoparticles via the decarboxylation of 1,3-dialkylimidazolium-2-carboxylate. These nanoparticles provided excellent activities and selectivities in the partial hydrogenation of alkynes into (Z)-alkenes under very mild reaction conditions.

As featured in:

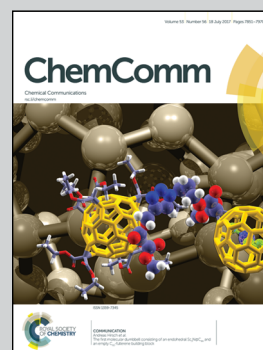

See Miriam Díaz de los Bernardos, Cyril Godard et al., *Chem. Commun.*, 2017, 53, 7894.



Cite this: *Chem. Commun.*, 2017, 53, 7894

Received 8th March 2017,
Accepted 27th April 2017

DOI: 10.1039/c7cc01779k

rsc.li/chemcomm


Facile synthesis of NHC-stabilized Ni nanoparticles and their catalytic application in the Z-selective hydrogenation of alkynes†

Miriam Díaz de los Bernardos,^{‡,*a} Sara Pérez-Rodríguez,^{‡,a} Aitor Gual,^a Carmen Claver^{id}^{ab} and Cyril Godard^{id}^{*ab}

Well defined Ni nanoparticles (NiNPs) stabilized with N-heterocyclic carbenes (NHCs) have been synthesized through a new methodology involving the decarboxylation of a zwitterionic CO₂ adduct. Their catalytic performance was tested in the partial hydrogenation of alkynes into (Z)-alkenes under very mild reaction conditions (50 °C and 5 bar H₂ pressure), providing excellent activities and selectivities.

Metal nanoparticles (MNPs) display unique physical and chemical properties, which endow them with high potential for applications in diverse areas such as medicine and catalysis, among others.^{1,2} To enhance their performance in catalysis, the selective formation of well-defined nano-objects is required. Furthermore, they should be stabilized with species that will restrict the approach of the substrate and as such induce selectivity. Nowadays, N-heterocyclic carbenes (NHCs) constitute one of the most versatile family of compounds in modern chemistry and are employed as ligands in transition metal catalysed transformations in both academia and the chemical industry.³ Although these ligands were used for the preparation of Au,^{4–8} Pd,⁹ Ir¹⁰ and Ru^{11,12} nanoparticles, to the best of our knowledge, there is only one report on the use of NHCs for the stabilization of Ni NPs.¹³ To date, NHC-stabilized MNPs have been obtained by three main methodologies: (i) by direct reduction of NHC-organometallic complexes,⁶ (ii) by procedures using the isolated free carbene (either by ligand exchange¹⁴ or by the organometallic approach developed by Chaudret¹¹), and (iii) using non-isolable carbenes *via in situ* generation of free carbenes (Scheme 1).¹²

In all cases, a basic pre-treatment of an imidazolium salt precursor is required, either for the isolation of the free carbene or for its *in situ* generation. Crabtree *et al.* reported the utilization of 1,3-dialkylimidazolium-2-carboxylate (**R₂Im-CO₂**) as an efficient

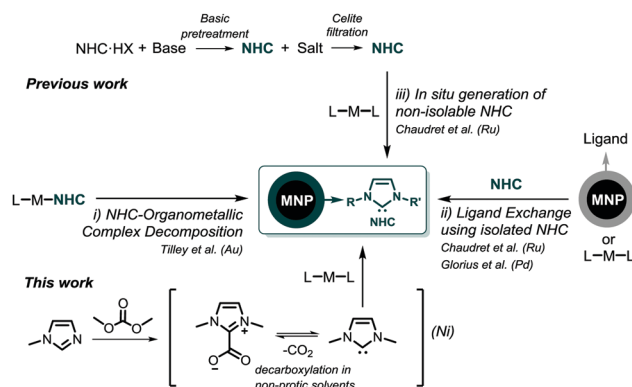

Scheme 1 Synthetic approaches to NHC-stabilized metal nanoparticles.

carbene precursor for the synthesis of NHC-based organometallic complexes.¹⁵

These imidazolium carboxylates are water-stable and synthetically readily available, and efficiently transfer the corresponding NHC ligand by decarboxylation in non-polar solvents.^{16,17} It was therefore thought that the use of such NHC-precursors could be applied in the synthesis of MNPs, and as such, neither the filtration of inorganic salts nor the isolation of carbenes would be required.

The hydrogenation of alkynes to selectively produce (*E*)- or (*Z*)-alkenes is a useful synthetic tool for the production of valuable compounds.¹⁸ Since classical heterogeneous catalysts are usually based on noble metals such as Pd, Pt or Au,^{19–22} new approaches employing abundant and low-cost metals are therefore desirable. Recently, Precht and co-workers reported the use of NiNPs stabilised with ionic liquids for the selective hydrogenation of alkynes to the corresponding (*Z*)-alkenes.²⁰

Here, we report a new and straightforward methodology to prepare small and well defined NHC-stabilized nickel nanoparticles, both colloidal and supported on carbon nanotubes (CNTs), using a simple “one-pot” procedure based on the decarboxylation of 1,3-dialkylimidazolium-2-carboxylate (**R₂Im-CO₂**).²³ This procedure avoids basic pre-treatment. The catalytic performance

^a Centre Tecnològic de la Química, Marcel·lí Domingo s/n, Campus Sescelades, 43007 Tarragona, Spain

^b Departament de Química Física i Inorgànica, Universitat Rovira i Virgili, Marcel·lí Domingo s/n, Campus Sescelades, 43007 Tarragona, Spain.
E-mail: Cyril.godard@urv.cat

† Electronic supplementary information (ESI) available. See DOI: 10.1039/c7cc01779k

‡ These authors contributed equally to the experimental work.




of the latter species was evaluated in the selective hydrogenation of internal alkynes into *Z*-alkenes under mild conditions.

To evaluate **Me₂Im-CO₂** as a ligand precursor for the stabilization of NiNPs, the organometallic precursor Ni(COD)₂ (COD = cyclooctadiene) was reduced in THF under 3 bar of hydrogen at 60 °C in the presence of **Me₂Im-CO₂** (Scheme 2). The amount of the NHC-based ligand used during the synthesis was varied: 0.1, 0.2, 0.5 and 1 equivalent per Ni.

In the presence of 0.1 equivalent of the ligand, nickel particles were not efficiently stabilized. When the amount of the ligand was increased, the NPs **Ni-0.2**, **Ni-0.5** and **Ni-1** were formed and could be isolated. The TEM images of these particles are shown in Fig. 1.

As previously observed with NHCs,¹¹ smaller NPs were formed upon increasing the amount of the ligand from 0.2 to 0.5 equivalent per Ni. Indeed, in the **Ni-0.2** sample, the NPs exhibited a mean diameter of *ca.* 2.4 ± 0.9 nm, whilst for **Ni-0.5**, the mean size was *ca.* 2.0 ± 0.4 nm. Under these conditions, the particles were well separated and neither agglomeration nor coalescence was detected on the carbon grid, indicating that the NHC-based ligand is strongly adsorbed on the nickel surface. However, for

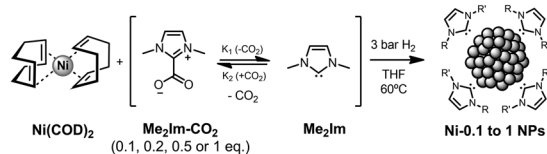

Scheme 2 Synthetic methodology used for the preparation of NHC-stabilized NiNPs using **Me₂Im-CO₂** as a stabilizer precursor.

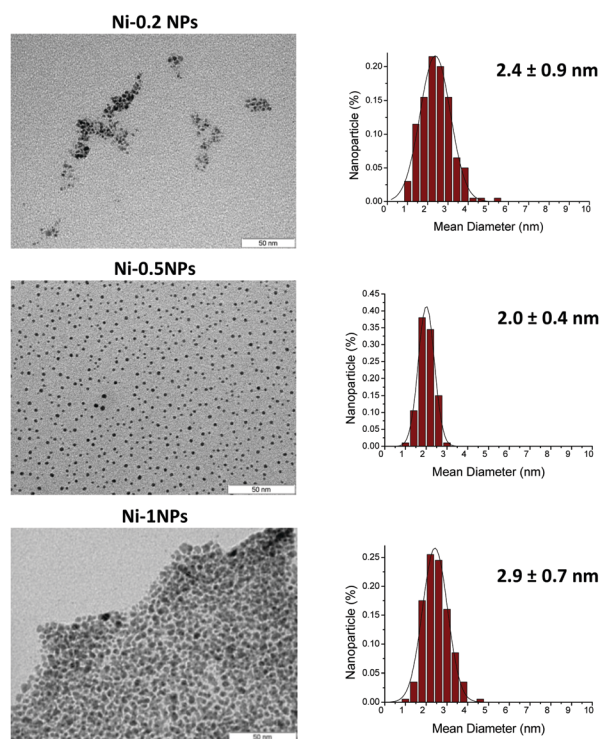


Fig. 1 TEM micrographs and size distributions of **Ni-0.2**, **Ni-0.5** and **Ni-1** nanoparticles.

Ni-1 NPs a mean diameter of *ca.* 2.9 ± 0.7 nm was measured and a high degree of agglomeration was observed.

TGA of the samples revealed that the NHC content for these NPs ranges from *ca.* 15 wt% (**Ni-0.2** NPs) to 44 wt% (**Ni-1.0** NPs) (Fig. S1, ESI†). **Ni-0.5** NPs presented a ligand content of 27 wt%. Similar NHC contents were previously reported for Ru²⁴ and Pt²⁵ NPs. In addition, no weight loss associated with the presence of imidazolium carboxylate (at *ca.* 200 °C) was observed, confirming that this species does not act as a stabilizer. XRD patterns of a selected sample (**Ni-0.5** NPs, Fig. S3, ESI†) revealed the presence of crystalline Ni with fcc packing. XPS measurements (Fig. S4, ESI†) showed a high percentage of NiO on the surface of the Ni nanoparticles (67.6 at%), which was attributed to nanoparticle oxidation during the sample preparation for XPS analysis. Indeed, nickel nanoparticles are very reactive and burn spontaneously in the presence of air, producing white clouds of the oxide, which is explained by their very small size and clean surface state. Upon Ar sputtering, the Ni content substantially increased (from 32.4 to 95.5 at%), confirming the presence of metal core nanoparticles. This new route was first validated by comparing two batches of NiNPs stabilized with 1,3-dimethylimidazol-2-ylidene (**Me₂Im**), prepared by (i) the abovementioned methodology and (ii) the reported *in situ* generation of non-isolable NHCs,¹² which is first employed here for the preparation of Ni nanoparticles. Following the last protocol, **Me₂Im-HCl** (0.5 molar equiv./Ni) was deprotonated *via* the addition of a slight excess of KOTBu in THF, and the resulting suspension (**Me₂Im**) was filtered through celite prior to its transfer into a solution of Ni(COD)₂ in THF. The reaction mixture was then pressurized with 3 bar of H₂, leading to a colloidal solution of nickel NPs with a mean size of 2.0 ± 0.5 nm (Fig. S5, ESI†). Comparison with the TEM data obtained by the new methodology clearly revealed similar dispersion of the particles on the grid and size (2.0 ± 0.4 nm). In addition, the IR spectra recorded for the two batches of **Ni-Me₂Im** NPs were similar. In the sample of NPs prepared *via* the decarboxylation method, the characteristic features of the **Me₂Im-CO₂** compound were not detected, confirming that this species does not participate in the NP stabilization (Fig. S6, ESI†). Furthermore, the TGA data recorded for the two batches of **Ni/Me₂Im** NPs showed similar profiles (Fig. S7, ESI†). Based on these results, it was concluded that both synthetic procedures yield very similar Ni nanoparticles, and thus evidenced that the new methodology developed in this work allows rapid access to NHC-stabilized nanoparticles without the need for a basic pre-treatment. With these results in hand, supported Ni nanocatalysts were synthesized following the same methodology in the presence of multiwalled carbon nanotubes (MWCNTs). The amount of the NHC-based ligand used during the synthesis was varied from 0.2 to 0.5 to 1 equivalent per Ni. TEM analysis of the resulting hybrid material is shown in Fig. 2. Interestingly, the TEM micrographs of **Ni-0.2@CNTs** and **Ni-0.5@CNTs** revealed the formation of very similar nanoparticles with no significant differences in size, shape and distribution since both exhibited a diameter of *ca.* 3.6 ± 0.8 nm.

It is remarkable that an increase of the mean particle size and size distribution was observed in comparison with the



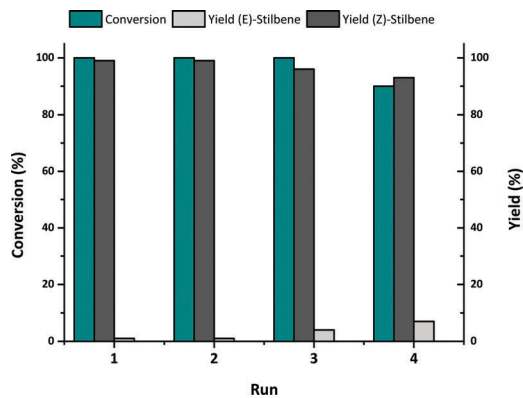


Fig. 5 Recycling experiment of the hydrogenation of diphenylacetylene over **Ni-0.5@CNTs** at 50 °C, 5 bar H₂ for 7 h.

The remaining solution after the catalytic reaction was analysed by inductively coupled plasma (ICP), revealing a nickel content of 0.008% with respect to all Ni initially introduced. Furthermore, no evolution of the reaction was observed when the semi-hydrogenation of diphenylacetylene was tested using the remaining solution of a catalytic test after filtration of the heterogeneous catalyst. These results indicated that no relevant leaching had taken place under the reaction conditions.

Next, we examined the application of the optimized catalyst system for a broader scope of internal alkynes (Table 1, entries 4–7). When 4-octyne was tested as a substrate (entry 4), the corresponding (*Z*)-alkene was again obtained in quantitative yield. However, when 2-octyne was used (entry 5), 81% conversion was measured and a mixture of alkene and alkane was observed. However, the *Z/E* ratio remained at *ca.* 98%. In the case of a 1-phenyl-1-butyne substrate, a greater amount of alkane was obtained (12%) at 100% conversion and the selectivity *Z/E* was slightly lower (*ca.* 92%) (entry 6). In the hydrogenation of 3-phenyl-2-propyn-1-ol (entry 7), the selective formation of the (*Z*)-alkene was observed, but 13% of the over-hydrogenated product was detected with full conversion.

To evaluate the robustness of these catalysts, **NiMe₂Im-0.5 NPs@CNTs** were recycled several times in the hydrogenation of diphenylacetylene as a model substrate (Fig. 5). Neither relevant loss of activity nor selectivity was observed over 3 runs although a slight decrease in activity was observed in the last run.

In conclusion, a new procedure for synthesizing small and well-defined NHC-stabilized NiNPs based on the decarboxylation of the corresponding imidazolium carboxylate zwitterionic salt has been developed. This methodology was employed for the synthesis of colloidal NiNPs and for the immobilization of NiNPs onto carbon nanotubes by a simple “one-pot” procedure without surface modification. These NPs were thoroughly characterised and the supported NPs revealed efficient catalysts in the

selective hydrogenation of terminal alkynes into the corresponding (*Z*)-alkenes under very mild reaction conditions. Furthermore, these heterogeneous catalysts can be readily recovered by simple filtration and reused 3 times without relevant decrease in activity.

The authors are grateful to the European Union’s Horizon 2020 research and innovation programme (ref. 677471), the TERRA project and the Ministerio de Economía y Competitividad and the Fondo Europeo de Desarrollo Regional FEDER (CTQ2016-75016-R, AEI/FEDER, UE) for funding.

Notes and references

- G. Schmid, *Nanoparticles*, From theory to applications, Weinheim, 2004.
- A. Roucoux, J. Schulz and H. Patin, *Chem. Rev.*, 2002, **102**, 3757–3778.
- M. N. Hopkinson, C. Richter, M. Schedler and F. Glorius, *Nature*, 2014, **510**, 485–496.
- D. Canseco-Gonzalez, A. Petronilho, H. Mueller-Bunz, K. Ohmatsu, T. Ooi and M. Albrecht, *J. Am. Chem. Soc.*, 2013, **135**, 13193–13203.
- E. C. Hurst, K. Wilson, I. J. S. Fairlamb and V. Chechik, *New J. Chem.*, 2009, **33**, 1837–1840.
- J. Vignolle and T. D. Tilley, *Chem. Commun.*, 2009, 7230–7232.
- A. V. Zhukhovitskiy, M. G. Mavros, T. Van Voorhis and J. A. Johnson, *J. Am. Chem. Soc.*, 2013, **135**, 7418–7421.
- G. Wang, A. Ruhling, S. Amirjalayer, M. Knor, J. B. Ernst, C. Richter, H.-J. Gao, A. Timmer, H.-Y. Gao, N. L. Doltsinis, F. Glorius and H. Fuchs, *Nat. Chem.*, 2017, **9**, 152–156.
- K. V. S. Ranganath, J. Kloesges, A. H. Schaefer and F. Glorius, *Angew. Chem., Int. Ed.*, 2010, **49**, 7786–7789.
- L. S. Ott, M. L. Cline, M. Deetlefs, K. R. Seddon and R. G. Finke, *J. Am. Chem. Soc.*, 2005, **127**, 5758–5759.
- P. Lara, O. Rivada-Wheelaghan, S. Conejero, R. Poteau, K. Philippot and B. Chaudret, *Angew. Chem., Int. Ed.*, 2011, **50**, 12080–12084.
- L. M. Martinez-Prieto, A. Ferry, P. Lara, C. Richter, K. Philippot, F. Glorius and B. Chaudret, *Chem. – Eur. J.*, 2015, **21**, 17495–17502.
- J.-F. Soule, H. Miyamura and S. Kobayashi, *J. Am. Chem. Soc.*, 2013, **135**, 10602–10605.
- C. Richter, K. Schaepe, F. Glorius and B. J. Ravoo, *Chem. Commun.*, 2014, **50**, 3204–3207.
- A. M. Voutchkova, L. N. Appelhans, A. R. Chianese and R. H. Crabtree, *J. Am. Chem. Soc.*, 2005, **127**, 17624–17625.
- J. D. Holbrey, W. M. Reichert, I. Tkatchenko, E. Bouajila, O. Walter, I. Tommasi and R. D. Rogers, *Chem. Commun.*, 2003, 28–29.
- D. M. Denning and D. E. Falvey, *J. Org. Chem.*, 2014, **79**, 4293–4299.
- J. G. de Vries and C. J. Elsevier, *The Handbook of Homogeneous Hydrogenation*, Wiley-VCH, 2008.
- M. Crespo-Quesada, F. Cardenas-Lizana, A.-L. Dessimoz and L. Kiwi-Minsker, *ACS Catal.*, 2012, **2**, 1773–1786.
- H. Konnerth and M. H. G. Prechtel, *Chem. Commun.*, 2016, **52**, 9129–9132.
- A. Molnar, A. Sarkany and M. Varga, *J. Mol. Catal. A: Chem.*, 2001, **173**, 185–221.
- E. Bayer and W. Schumann, *J. Chem. Soc., Chem. Commun.*, 1986, 949–952.
- E. J. Garcia-Suarez, A. M. Balu, M. Tristany, A. B. Garcia, K. Philippot and R. Luque, *Green Chem.*, 2012, **14**, 1434–1439.
- P. Lara, L. M. Martinez-Prieto, M. Rosello-Merino, C. Richter, F. Glorius, S. Conejero, K. Philippot and B. Chaudret, *Nano-Struct. Nano-Objects*, 2016, **6**, 39–45.
- E. A. Baquero, S. Tricard, J. C. Flores, E. de Jesus and B. Chaudret, *Angew. Chem., Int. Ed.*, 2014, **53**, 13220–13224.

